

TEST REPORT

(Electronic version)

检测报告



VERIFICATION WEBSITE: www.gttc.net.cn

VERIFICATION CODE: [REDACTED]

No: [REDACTED]

ISSUE DATE: 2020-05-06

APPLICANT: [REDACTED]
ADDRESS: [REDACTED]
[REDACTED]

INFORMATION CONFIRMED BY APPLICANT:

KN95 MASK
QUANTITY: EIGHTY PIECES

DATE RECEIVED/DATE TEST STARTED: 2020-05-04

CONCLUSION:

VISUAL FIELD	M
FILTRATION EFFICIENCY TO NaCl PARTICULATE MATTER	M
INSPIRATORY RESISTANCE	M
EXPIRATORY RESISTANCE	M
FLAMMABILITY	M
HEAD BAND	M

NOTE: "M" -MEET THE STANDARD'S REQUIREMENT "F" -FAIL TO MEET THE STANDARD'S REQUIREMENT
"----" -NO COMMENT

REMARK:

THIS REPORT IS THE ENGLISH TRANSLATION VERSION OF THE REPORT [REDACTED]
ALL THE TESTED ITEMS ARE TESTED UNDER THE STANDARD CONDITION (EXCEPT FOR INDICATION).
COPIES OF THE REPORT ARE VALID ONLY RE-STAMPED.
THE EXPERIMENT WAS CARRIED OUT AT No. 1, ZHUJIANG ROAD, PANYU DISTRICT, GUANGZHOU, GUANGDONG, P. R. CHINA.

APPROVED BY:
ZiShan Guo SENIOR ENGINEER


郭子山



TEST REPORT

(Electronic version)

No: XXXXXXXXXX

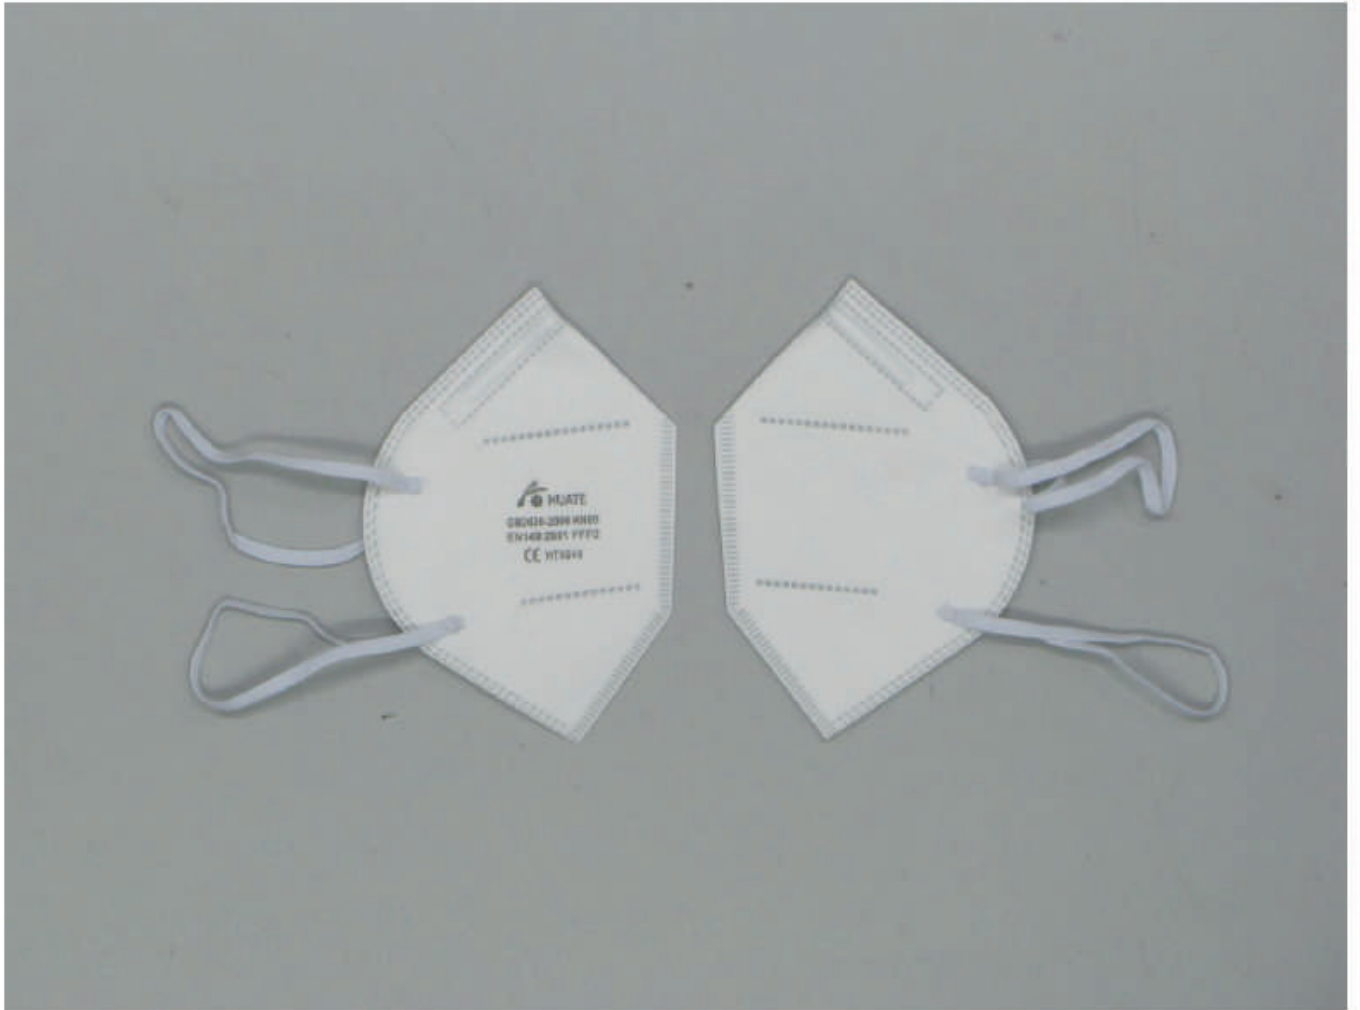

TEST REPORT

(Electronic version)

No: XXXXXXXXXX

VISUAL FIELD(°)
(GB 2890-2009 6.8)

70

REQUIREMENT
≥ 60
(GB 2626-2006)

FILTRATION EFFICIENCY TO NaCl PARTICULATE MATTER (%)

(GB 2626-2006 6.3, AIR FLOW:85L/min, AEROSOL:NaCl, AEROSOL CONCENTRATION, 15mg/m³,
TEMP:22.4℃ RH:36.8%)

FILTRATION EFFICIENCY:
UNTREATED SAMPLE

1# 99.345
2# 99.210
3# 99.372
4# 99.418
5# 99.470
6# 99.205
7# 99.281
8# 99.306
9# 99.455
10# 99.403

REQUIREMENT
FILTRATION EFFICIENCY:
≥ 95.0
(KN95)
(GB 2626-2006)

CONDITIONING TREATED

1# 99.241
2# 99.078
3# 99.134
4# 99.086
5# 99.372

INSPIRATORY RESISTANCE (Pa)

(GB 2626-2006 6.5, HEAD SIZE: MEDIUM)

UNTREATED SAMPLE:

1# 151.1
2# 148.6

PRETREATMENT SAMPLE:

1# 135.5
2# 137.4

REQUIREMENT
≤ 350
(GB 2626-2006)

EXPIRATORY RESISTANCE (Pa)

(GB 2626-2006 6.6, HEAD SIZE: MEDIUM)

UNTREATED SAMPLE:

1# 138.3
2# 131.4

PRETREATMENT SAMPLE:

1# 118.8
2# 123.7

REQUIREMENT
≤ 250
(GB 2626-2006)



PAGE 3 OF 4

TEST REPORT

(Electronic version)

No: XXXXXXXXXX

FLAMMABILITY (s)

(GB 2626-2006 6.15)

AFTERFLAME TIME
UNTREATED SAMPLE

1# 0.0

2# 0.0

CONDITIONING TREATED

3# 0.0

4# 0.0

REQUIREMENT

AFTERFLAME TIME

≤5

(GB 2626-2006)

HEAD BAND

(GB 2626-2006 6.11)

UNTREATED SAMPLE:

1# PASS

CONDITIONING TREATED:

1# PASS

REQUIREMENT

EACH HEAD BAND, BUCKLE AND OTHER ADJUST

PARTS OF MASK SHOULD NOT SLIP OR BREAK

UNDER 10N TENSION FOR 10S.

(GB 2626-2006)



—End of Report—

PAGE 4 OF 4